

Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE 2009		2. REPORT TYPE		3. DATES COVERED 00-00-2009 to 00-00-2009	
4. TITLE AND SUBTITLE Relation Between Strucutral and Optical Properties of InN and InxGa1-xN Tin Films				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) University of California, Berkeley,Materials Science & Engineering,Berkeley,CA,94720				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT Same as Report (SAR)	18. NUMBER OF PAGES 3	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			



Title:

Relation between structural and optical properties of InN and In_xGa_{1-x}N thin films

Author:

[Liliental-Weber, Z.](#), [Zakharov, D.N.](#), [Jasinski, J.](#), [Yu, K.M.](#), [Wu, J.W.](#), [Ager III, J.W.](#), et al.

Publication Date:

05-21-2008

Publication Info:

Lawrence Berkeley National Laboratory

Permalink:

<http://www.escholarship.org/uc/item/5b64p0jc>

Citation:

Liliental-Weber, Z., Zakharov, D.N., Jasinski, J., Yu, K.M., Wu, J.W., Ager III, J.W., et al. (2008). Relation between structural and optical properties of InN and In_xGa_{1-x}N thin films. Lawrence Berkeley National Laboratory: Lawrence Berkeley National Laboratory. LBNL Paper LBNL-56492. Retrieved from: <http://www.escholarship.org/uc/item/5b64p0jc>

Keywords:

InN InGa_N structural and optical properties

Abstract:

Transmission Electron Microscopy (TEM) and optical measurements obtained from InN and In_{1-x}Ga_xN films (0 < x < 0.54) grown by Molecular Beam Epitaxy are presented. Energy gaps measured by absorption, PR, and PL for InN films grown on c-plane Al₂O₃ were in the range of 0.7 eV. No In or other inclusions were observed in these films, ruling out the possibility of a strong Mie scattering mechanism. In the In_{1-x}Ga_xN films the relationship between the structural properties and the optical properties, in particular the presence or absence of a Stokes shift between absorption and PL, is discussed. TEM studies show that high quality layers do not have a Stokes shift. Some films had compositional ordering; these films also showed a shift between absorption edge and luminescence peak.



Relation Between Structural and Optical Properties of InN and $\text{In}_x\text{Ga}_{1-x}\text{N}$ Thin Films

Z. Liliental-Weber^a, D. N. Zakharov^a, J. Jasinski^{a,b}, K. M. Yu^a, J. Wu^{a,c},
J.W. Ager III^a, W. Walukiewicz^a, E.E. Haller^{a,c}, H. Lu^d, S. X. Li^{a,c}, and
W. J. Schaff^d

^aMaterials Sciences Division, Lawrence Berkeley National Lab, Berkeley, CA 94720

^bcurrent address: School of Engineering, University of California, Merced, Merced, CA 95344

^cMaterials Science and Engineering, University of California, Berkeley, Berkeley, CA 94720

^dDepartment of Electrical and Computer Engineering, Cornell University, Ithaca, NY 14853

Transmission Electron Microscopy (TEM) and optical measurements obtained from InN and $\text{In}_{1-x}\text{Ga}_x\text{N}$ films ($0 < x < 0.54$) grown by Molecular Beam Epitaxy are presented. Energy gaps measured by absorption, PR, and PL for InN films grown on c-plane Al_2O_3 were in the range of 0.7 eV. No In or other inclusions were observed in these films, ruling out the possibility of a strong Mie scattering mechanism. In the $\text{In}_{1-x}\text{Ga}_x\text{N}$ films the relationship between the structural properties and the optical properties, in particular the presence or absence of a Stokes shift between absorption and PL, is discussed. TEM studies show that high quality layers do not have a Stokes shift. Some films had compositional ordering; these films also showed a shift between absorption edge and luminescence peak.

INTRODUCTION

Indium group III-nitride materials are currently under intense investigation mainly due to the controversy in material properties such as the bandgap. The bandgap for InN was originally reported as 1.9 eV [1] but recent optical measurements show that this value is close to 0.7 eV [2]. Earlier grown materials showed however, very high electron densities [3]. Recently grown MBE films have electron densities in the range of $1 \times 10^{18} \text{ cm}^{-3}$ down to $3 \times 10^{17} \text{ cm}^{-3}$. All low electron density materials showed a small bandgap. It has been claimed that In-rich clusters are formed in this material and are responsible for an apparent lower bandgap [4]. In-containing nitrides are very important for application in devices but the large size difference between Ga and In atoms can lead to a spinodal decompositions. Both theoretical and experimental evidences were reported [5,6].

In this paper we want to describe the structural and optical quality of the $\text{In}_{1-x}\text{Ga}_x\text{N}$ ($0 < x < 0.54$) grown by Molecular Beam Epitaxy. Transmission Electron Microscopy (TEM), Photoluminescence (PL) and photoabsorption have been used for these studies.

EXPERIMENTAL

Several $\text{In}_{1-x}\text{Ga}_x\text{N}$ with x up to 0.54 samples have been studied. InN film in which low (0.7 eV) bandgaps were measured were evaluated in order to

verify the presence or absence of In inclusions. Growth details were described earlier [7].

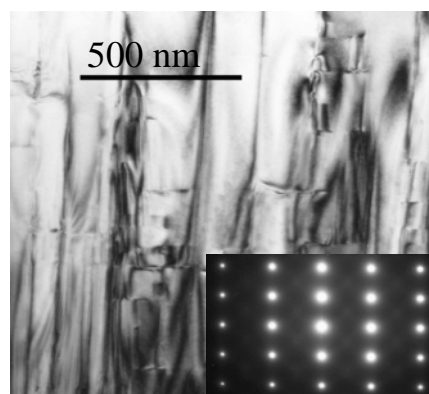


Fig. 1. Bright field image of InN with a small bandgap. Threading dislocations and dislocation loops on c-plane are observed, the inset shows diffraction pattern consistent with InN lattice spacings.

Transmission Electron Microscopy (TEM) studies using classical bright field, high resolution and electron diffraction of InN grown on c-plane indicate that there are no In or other inclusions observed in these films, ruling out the possibility of a strong Mie scattering mechanism (Fig. 1) The observed contrast in the film was uniform and no indication of inclusion was observed. Electron diffraction taken from different areas show only spots consistent with InN (Fig. 1-inset), without any extra spots which would be

characteristic for other phases. Dislocation densities were typically in the mid- 10^{10}cm^{-2} range with majority of edge dislocations.

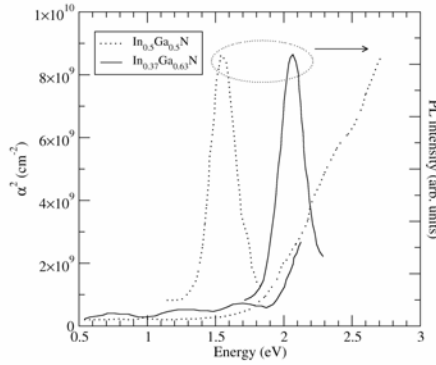


Fig. 2. PL and absorption spectra showing that the “Stokes shift” can be reduced to < 0.1 eV in recently grown high structural quality films (solid lines). The samples with 0.5 eV shift show compositional ordering.

Some samples of the $\text{In}_{1-x}\text{Ga}_x\text{N}$ films grown on thick AlN layer deposited on Al_2O_3 show a Stokes shift (Fig. 2) by about 0.5 eV measured from the absorption edge and room-temperature photoluminescence peak. The samples where this shift is not observed show high structural quality with dislocation density about $6 \times 10^{10}\text{cm}^{-2}$.

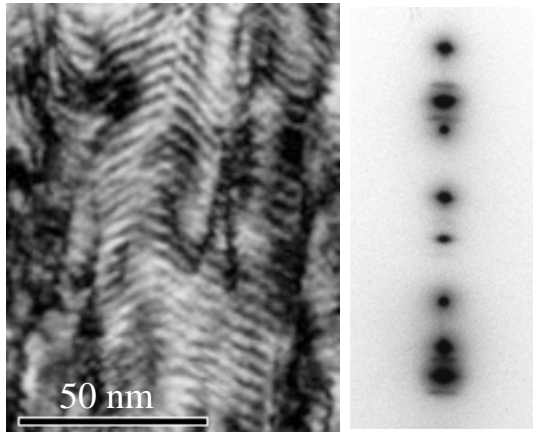


Fig. 3. (a) Bright field image of the $\text{In}_{1-x}\text{Ga}_x\text{N}$ with $x=0.5$. Density of dislocations in this layer was estimated $\sim 1 \times 10^{11}\text{cm}^{-2}$. Note equally distanced (45\AA) fringes due to compositional ordering. (b) Magnified part of the central row of the electron diffraction spots along c-axis (just above the primary beam) showing arrangement of the spots from the Al_2O_3 substrate, AlN buffer layer and the $\text{In}_{1-x}\text{Ga}_x\text{N}$ together with the extra spots forming the arcs around the $\text{In}_{1-x}\text{Ga}_x\text{N}$ spots.

In the samples where this shift was observed ($x=0.5$) compositional ordering was observed (Fig. 3a).

Equally distanced fringes were observed in the entire $\text{In}_{1-x}\text{Ga}_x\text{N}$ film. Electron diffraction (Fig. 3b) shows extra spots distributed in a form of small arcs indicating that these fringes do not remain on particular planes but locally vary from plane to plane. The distance between these fringes ($\sim 45\text{\AA}$) stays approximately constant. The estimated lattice constant of this $\text{In}_{1-x}\text{Ga}_x\text{N}$ layer is $a=3.43\text{\AA}$ and $c=5.46\text{\AA}$, indicating composition layer extremely close to this given by the crystal grower ($x=0.5$).

CONCLUSIONS

In conclusion we can confirm using TEM studies that our InN samples which show low bandgap (~ 0.7 eV) do not have In inclusions, therefore Mie scattering can be excluded as a mechanism responsible for this low value. For high quality $\text{In}_{1-x}\text{Ga}_x\text{N}$ samples grown by MBE on thick AlN buffer layer the Stokes shift between an absorption edge and photoluminescence was not observed (< 0.1 eV). However, for the $x=0.5$ compositional modulation was observed leading to a Stokes shift, most possible due to two different band edges for InN and GaN driven by strain between the AlN buffer and the $\text{In}_{1-x}\text{Ga}_x\text{N}$.

ACKNOWLEDGMENTS

This work was supported by the U.S. Department of Energy under contract DE-AC03-76SF00098. The use of the facility at the national Center for Electron Microscopy at the LBNL is greatly appreciated. Cornell group acknowledges the support of Colin Wood of the Office of Naval research under the contract N000149910936.

REFERENCES

1. T. A. Tansley and C.P. Foley, J. Appl. Phys. 59, 3241 (1986).
2. J. Wu, W. Walukiewicz, K.M. Yu, J. W. Ager III, E.E. Haller, H. Lu, W. J. Schaff, Y. Saito, and Y. Nanishi, Appl. Phys. Lett. 80, 3967 (2002).
3. A.G. Bhuiyan, A. Hashimoto, and A. Yamamoto, Appl. Phys. Lett. 94, 2779 (2003).
4. T. V. Shubina, S. V. Ivanov, V.N. Jmerik, D.D. Solnyshkov, V. A. Vekshin, P. S. Kop'ev, A. Vasson, J. Lemarie, A. Kavokin, H. Amano, K. Shimono, A. Kasic, and B. Monemar, Phys. Rev. Lett., 92, 117407 (2004).
5. I.H. Ho and G.B. Stringfellow, Appl. Phys. Lett. 69, 2701 (1996).
6. A. N. Westmeyer and S. Mahajan, Appl. Phys. Lett., 79, 2710 (2001).
7. H. Lu, W.J. Schaff, J. Hwang, H. Wu, W. Yeo, A. Pharkya, and L.F. Eastman, Appl. Phys. Lett., 77, 2548 (2000).